



UNIVERSAL WISER
PUBLISHER

Multi-objective Optimization of Welding Parameters of Pulsed Current Micro Plasma Arc Welded AISI 904L Super Austenitic Steel

M. Sailaja^{1*}, K. Ramji²

¹Department of Mechanical Engineering, Anil Neerukonda Institute of Technology and Sciences, Visakhapatnam, India

²Department of Mechanical Engineering, Andhra University, Visakhapatnam, India

¹Email: saisailaja2k@gmail.com

²Email: ramjidme@gmail.com

Abstract: In the present work, AISI 904L super austenitic steel sheets of 0.4mm thick is butt welded using Micro Plasma Arc Welding. Welding input parameters like peak current, base current, pulse rate and pulse width are considered and output responses like fusion zone grain size, hardness and ultimate tensile strength of the welded joint are considered. 31 experiments are performed as per Central Composite Design (CCD) design matrix of Response Surface Method (RSM) by considering four factors and five levels of weld input parameters. Grey Relational Analysis (GRA) is carried out by minimizing fusion zone grain size and maximizing fusion zone hardness and ultimate tensile strength to find the optimal combination of weld input parameters. The order of importance of weld input parameters are also identified and improvement in Grey Relational Grade was found.

Keywords: Micro Plasma Arc Welding, AISI 904L, RSM, Grey Relational Analysis

1. Introduction

Stainless steels are well known metal alloy for corrosion resistance. All stainless steels are iron base alloy consist 10% or more chromium. Chromium is the major element which responsible for corrosion resistance, although other elements, particularly nickel and molybdenum, are added to improve corrosion resistance. There are different types of stainless steels that are currently available one of those is austenitic stain less steel.

Austenitic stainless steels are the common and familiar type of stainless steel they are most easily recognized as nonmagnetic and they are widely used in various industries as structural material, as they possess a combination of properties like high strength and ductility, good formability and versatile fabricability^[1].

Super austenitic stainless steels are highly alloyed iron-nickel-chromium stainless steel, containing molybdenum have been developed to respond to severe corrosion specifications. Superaustenitic stainless steels exhibit great resistance to chloride pitting and crevice corrosion because of high molybdenum content, and the higher nickel content ensures better resistance to stress-corrosion cracking^[2-3]. Super-austenitic stainless steels are widely used in marine, petrochemical and nuclear industries due to their excellent strength and corrosion resistance, and are preferred in aggressive environments. It has been reported that these steels have improved properties such as weldability, formability compared to the conventional stainless steels^[4-6].

AISI 904L is a kind of super austenitic stainless steel, which has high strength, high hardness, good impact toughness and welding performance with low carbon, high nickel, chromium, and a small amount of copper alloy system^[7,8]. The joining of super austenitic stainless steel can be done with several welding process but, for thin sheets previous researches proved that pulsed current micro plasma arc welding provides good mechanical properties without damaging metal sheets^[9-11].

In the present work Pulsed Current Micro Plasma Arc Welding (MPAW) is used to join AISI 904L super austenitic steel sheets of 0.4 mm thick. Welding input parameters like peak current, base current, pulse rate and pulse width are considered and output responses like fusion zone grain size, hardness and ultimate tensile strength of the welded joint are considered. The objective of the paper is to optimize welding parameters namely peak current, base current, pulse rate and pulse width in order to minimize fusion zone grain size and maximize fusion zone hardness and ultimate tensile strength using Grey Relational Analysis.

Copyright ©2019 M. Sailaja, et al.

DOI: <https://doi.org/10.37256/est.11202044>

This is an open-access article distributed under a CC BY license
(Creative Commons Attribution 4.0 International License)

<https://creativecommons.org/licenses/by/4.0/>

2. Experimentation

AISI 904L super austenitic steel of 0.4 mm thick sheets of 100 x 150 x 0.4 mm are welded autogenously with square butt joint without edge preparation. The chemical composition and tensile properties of AISI 904L sheets of 0.4 mm thick sheet is given in Table 1 & 2. High purity argon gas (99.99%) is used as a shielding gas and a trailing gas right after welding to prevent absorption of oxygen and nitrogen from the atmosphere. The welding has been carried out under the welding conditions presented in Table 3. There are many influential process parameters which effect the weld quality characteristics of Pulsed Current MPAW process like peak current, back current, pulse rate, pulse width, flow rate of shielding gas, flow rate of purging gas, flow rate of plasma gas, welding speed etc. From the earlier works ^[12-14] carried out on Pulsed Current MPAW it was understood that the peak current, back current, pulse rate and pulse width are the dominating parameters which effect the weld quality characteristics. The values of process parameters used in this study are the optimal values obtained from our earlier papers ^[12-14]. Hence peak current, back current, pulse rate and pulse width are chosen and their values are presented in Table 4. Details about experimental setup are shown in Figure 1.



Figure 1. Micro Plasma Arc Welding Setup

Table 1. Chemical composition of AISI 904L (weight %)

C	Mn	Cr	Ni	Mo	Cu	N	Fe
0.0074	1.56	19.92	24.75	4.33	1.43	0.069	47.9336

Table 2. Tensile properties of AISI 904L

Elongation(%)	YieldStrength (MPa)	UltimateTensile Strength (Mpa)	Hardness (VHN)
36	220	573	242

Table 3. Welding conditions

Power source	Secheron Micro Plasma Arc Machine (Model: PLASMAFIX 50E)
Polarity	DCEN
Mode of operation	Pulse mode
Electrode	2% thoriated tungsten electrode
Electrode Diameter	1 mm
Plasma gas	Argon & Hydrogen
Plasma gas flow rate	6 Lpm
Shielding gas	Argon
Shielding gas flow rate	6 Lpm
Purging gas	Argon
Purging gas flow rate	4Lpm
Copper Nozzle diameter	1mm
Nozzle to plate distance	1mm
Welding speed	230 mm/min
Torch Position	Vertical
Operation type	Automatic

Table 4. Process parameters and their limits

	Levels				
	-2	-1	0	+1	+2
Peak Current (Amperes)	16	18	20	22	24
Base Current (Amperes)	8	9	10	11	12
Pulse Rate (Pulses/sec)	30	40	50	60	70
Pulse Width (%)	40	50	60	70	80

2.1 Measurement of Grain Size

Three metallurgical samples are cut from each joint leaving the edges of defective portion of the welded length. Defective length of weld is identified visually and also by conducting dye penetrant and X-ray tests and mounted using Bakelite. Sample preparation and mounting is done as per ASTM E 3-1 standard. The transverse face of the samples are surface ground using 120 grit size belt with the help of belt grinder and polished sequentially using grade 1/0 (245 mesh size), grade 2/0 (425 mesh size) and grade 3/0 (515 mesh size) sand paper. The specimens are further polished using aluminum oxide, diamond paste and velvet cloth on a disc polishing machine. The polished specimens are macro-etched using aquaregia solution (three parts HCl and one part HNO₃) to reveal the microstructure.

By varying the etching time microstructure and grain size of the weld zone are revealed. The micrograph of heat affected zone is shown in Figure 2 and weld fusion zone is shown in Figure.3 at 100 X magnifications. The grain sizes are measured randomly in the weld heat affected zone (HAZ), as failure takes place in this region for most of the weld samples and the measured values are presented in Table 5.

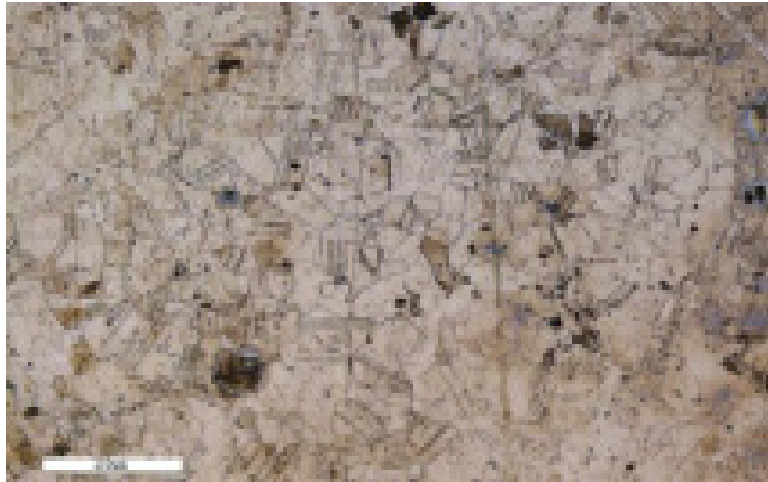


Figure 2. Microstructure of heat effected zone

From figure 3, it is understood that the weldments consist of a columnar dendritic structure. A pronounced acicular δ -ferrite formation (dark etching) is observed around the cellular dendritic austenitic grain.

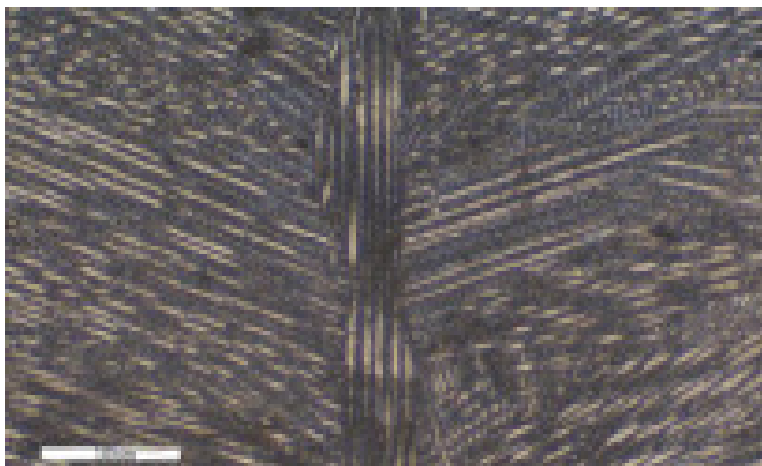


Figure 3. Microstructure of weld fusion zone



Figure 4. Microstructure of weld fusion zone and HAZ

2.2 Measurement of Fusion Zone Hardness

The hardness of the weld fusion zone of the welded samples are measured using Vicker's micro hardness testing machine (Make: METSUZAWA CO LTD, JAPAN, Model: MMT-X7) by applying a load of 0.5 Kg as per ASTM E384. Average values of three readings of each sample are presented in Table 5. Hardness was measured across the weld fusion zone (FZ) with a dwell time of 30 seconds and at an interval of 0.3 mm.

2.3 Measurement of Ultimate Tensile Strength (UTS)

Tensile specimens are prepared as per ASTM E8M-04 guidelines using wire cut Electro Discharge Machining (Figure 5) in the transverse direction of the weld from each welded sample. Tensile tests are carried out on 100 KN computer controlled Universal Testing Machine (Model No: 9036TD, Sr.No.STS-522, Star Testing Systems). The specimen is loaded at a rate of 1.5 KN/min as per ASTM specifications, so that the tensile specimens undergo deformation. From the stress strain curve (Figure 6), the ultimate tensile strength of the weld joints is evaluated and the average of the results of each sample is presented in Table 5.

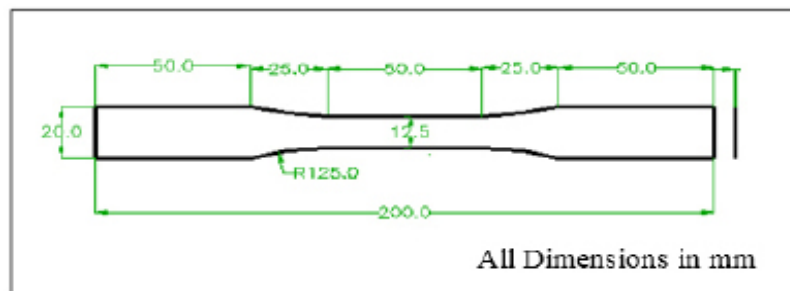


Figure 5. Tensile specimen as per ASTM E8M-04

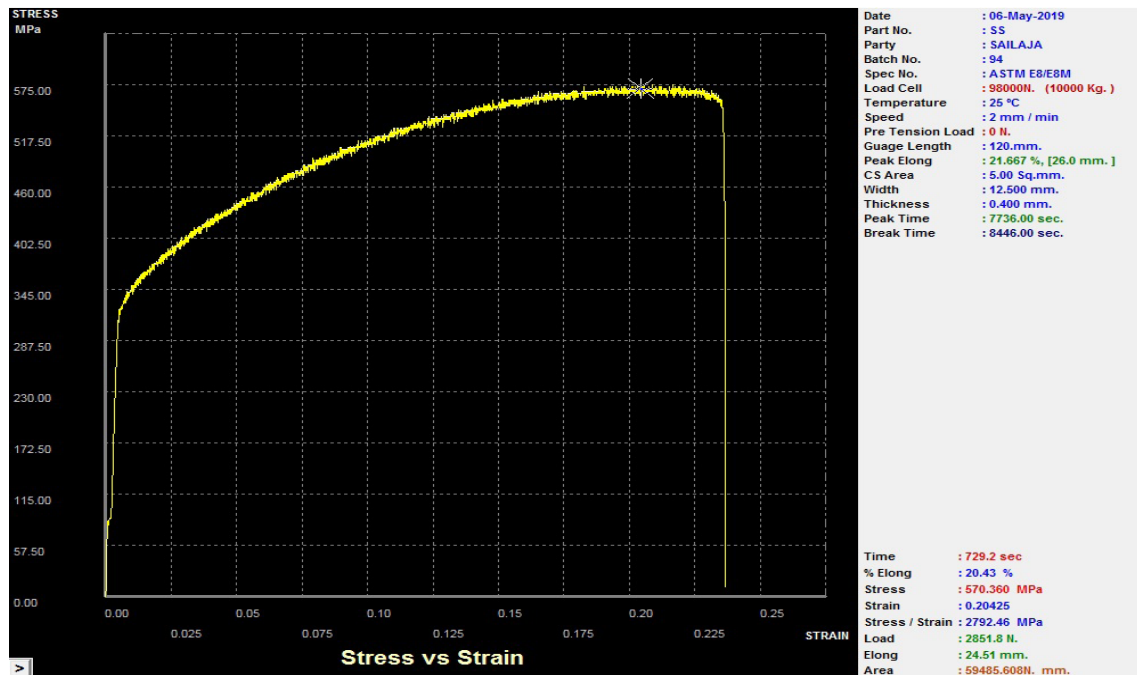


Figure 6. Stress strain curve

Table 5. Experimental Results

Sl. No	INPUT PARAMETERS				OUTPUT PARAMETERS EXPERIMENTAL		
	Peak Current (Amperes)	Base Current (Amperes)	Pulse Rate (Pulses/sec)	Pulse Width (%)	Grain size (Microns)	Hardness (VHN)	UTS (MPa)
1	18	9	40	50	68.4	257	530
2	22	9	40	50	67.6	266	554
3	18	11	40	50	70.2	267	538
4	22	11	40	50	68.3	277	546
5	18	9	60	50	70.8	255	530
6	22	9	60	50	73.9	263	540
7	18	11	60	50	69.4	269	524
8	22	11	60	50	70.8	279	542
9	18	9	40	70	76.2	255	518
10	22	9	40	70	68.4	259	528
11	18	11	40	70	73.4	255	526
12	22	11	40	70	66.4	276	546
13	18	9	60	70	76.4	247	522
14	22	9	60	70	68.8	249	540
15	18	11	60	70	70.2	253	532
16	22	11	60	70	63.6	273	546
17	16	10	50	60	75.8	247	506
18	24	10	50	60	66.8	262	547
19	20	8	50	60	72.6	251	518
20	20	12	50	60	66.8	277	542
21	20	10	30	60	68.6	265	540
22	20	10	70	60	70.8	261	534
23	20	10	50	40	69.6	271	548
24	20	10	50	80	71.12	255	527
25	20	10	50	60	70.6	265	539
26	20	10	50	60	69.8	267	537
27	20	10	50	60	70.6	265	539
28	20	10	50	60	68.8	267	537
29	20	10	50	60	69.6	265	539
30	20	10	50	60	68.8	267	537
31	20	10	50	60	70.2	269	540

3. Optimization

3.1 Optimal Solution from RSM

Figure 7 indicates the optimal solution of Response Surface method for minimum grain size and maximum hardness and UTS. From the figure, it is understood that at peak current 24 Amperes, base current 12 Amperes, pulse rate 70 pulses/sec and pulse width 80%, the optimal grain size of 49.7257 microns, hardness of 270.0476 VHN and UTS of 558.4762 MPa is obtained.

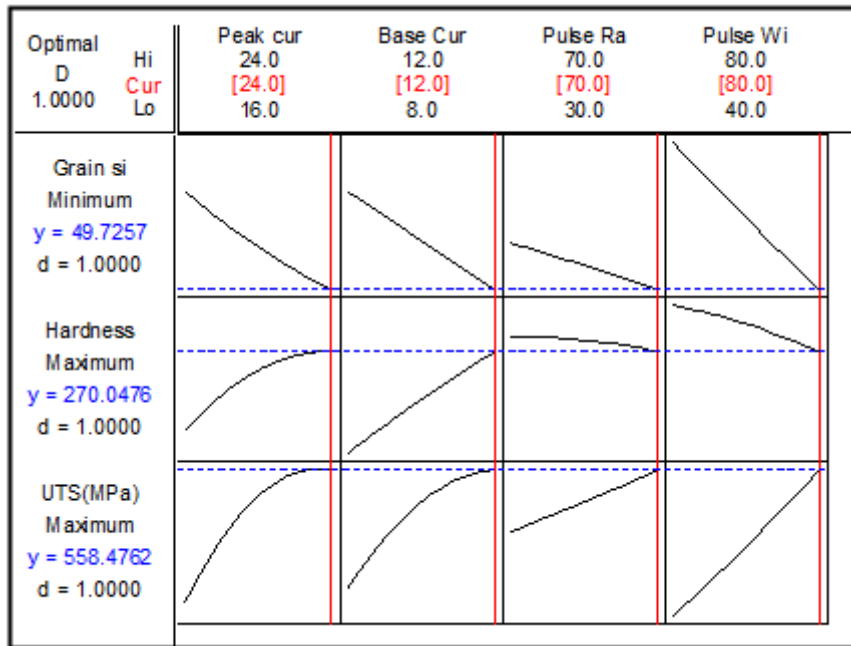


Figure 7. Optimal solution of Surface Response Method

3.2 Grey Relational Analysis

The grey system theory was proposed by Deng. The grey means the primitive data with poor, incomplete and uncertain information in the grey systematic theory. The incomplete relation of information among these data is called the grey relation. Grey relational analysis can effectively be recommended as an algorithm for optimising the complicated inter-relationships among multiple performance characteristics. Through the grey relational analysis, a grey relational grade is obtained to evaluate the multiple performance characteristics. As a result, optimisation of the complicated multiple performance characteristics can be converted into the optimisation of a single grey relational grade.

In grey relational analysis, experimental data i.e. measured features of quality characteristics are first normalized ranging from zero to one. The process is known as grey relational generation. Next, based on normalized experimental data, grey relational coefficient is calculated to represent the correlation between the desired and actual experimental data. Then overall grey relational grade is determined by averaging the grey relational coefficient corresponding to selected responses. The overall performance characteristic of the multiple response process depends on the calculated grey relational grade. This approach converts a multiple response process optimisation problem into a single response optimisation situation with the objective function as overall grey relational grade. The optimal parametric combination is then evaluated which would result into highest grey relational grade. The steps followed in the optimisation process are:

(i) Normalizing the experimental responses for all the trials.

The normalized expression (1) corresponding to smaller-the-better criteria is:

$$y_i(k) = \frac{\max x_i(K) - x_i(K)}{\max x_i(K) - \min x_i(K)} \quad (1)$$

where, $k=1$ to n ; $i=1$ to 25 , n is the performance characteristic and i is the trial number.

The normalized expression corresponding to larger-the-better criteria is:

$$y_i(k) = \frac{x_i(K) - \min x_i(K)}{\max x_i(K) - \min x_i(K)} \quad (2)$$

where $y_i(k)$ is the value after grey relational generation, $\min x_i(k)$ is the smallest value of $x_i(k)$ for k^{th} response and \max

$x_i(k)$ is the largest value of $x_i(k)$ for the k^{th} response.

(ii) Evaluation of Grey relational coefficient (γ).

$$\gamma[y_0(K), y_i(K)] = \frac{\Delta_{\min} + \zeta \cdot \Delta_{\max}}{\Delta_{0i}(K) + \zeta \cdot \Delta_{\max}} \quad (3)$$

where $\Delta_{0i}(K) = |y_0(K) - y_i(K)|$ is the absolute value of the difference between $y_0(K)$ and $y_i(K)$

$$\Delta_{\min} = \min \Delta_{0i}(K)$$

$$\Delta_{\max} = \max \Delta_{0i}(K)$$

ζ = distinguished coefficient

(iii) Calculating the Grey relational grade by averaging the Grey relational coefficient.

$$\xi_i = \frac{1}{n} \sum_{k=1}^n \gamma_i(K) \quad (4)$$

3.3 Analysis of Grain Size, Hardness, UTS

The specific targets in the present work are maximum hardness and UTS, minimize grain size. The above targets are prepared according to the specific requirements for manufacturing thin walled metal bellow. Initially, using Equations (1) and (2), experimental data have been normalized to obtain Grey relational generation. The normalized data and Δ_{0i} for each of the responses of bead geometry have been furnished in Table 6. The distinguishing coefficient ζ is substituted into Equation-2 to produce the gray relational coefficient. If all the process parameters are of equal weight, then ζ becomes 0.5. The gray relational coefficients and grade values for each experiment of the design matrix are calculated by applying the Equations 2 and 3 and tabulated (Table 7).

To find out the optimum process parameters and their effects on selected output parameters, the mean of the Grey relational grade for each level of the parameter is required. Table 7 indicates the mean of overall grey relational grades. The larger the value of the Grey relational grade, the better is the multi response characteristics. Therefore, the optimal level of the welding parameters is the level with the greatest grey relational grade value. The optimal performance for grain size, hardness and UTS are obtained for the following combination of input parameters: Peak current 22 Amps, Back Current 11 Amps, Pulse Rate 60 pulses/sec, Pulse Width 70 %.

Figure 8 indicates the effect of welding parameters on the multi-performance characteristics and the response graph of each level of the welding parameters for the performance. The higher values in Table 8 give the desired quality characteristic. Also, the maximum and minimum values of the grey relational grade show the importance of individual parameter in pulsed current MPAAW process. Hence, the order of importance of the welding parameters is base current, peak current, pulse width and pulse rate.

Table 6. Grey relational generation and Δ_{0i} of each performance characteristics

Exp. No.	Normalized			Deviation Sequence (Δ_{0i})		
	Grain size	Hardness	UTS	Grain size	Hardness	UTS
1	0.6250	0.3125	0.5000	0.3750	0.6875	0.5000
2	0.6875	0.5938	1.0000	0.3125	0.4063	0.0000
3	0.4844	0.6250	0.6667	0.5156	0.3750	0.3333
4	0.6328	0.9375	0.8333	0.3672	0.0625	0.1667
5	0.4375	0.2500	0.5000	0.5625	0.7500	0.5000
6	0.1953	0.5000	0.7083	0.8047	0.5000	0.2917
7	0.5469	0.6875	0.3750	0.4531	0.3125	0.6250
8	0.4375	1.0000	0.7500	0.5625	0.0000	0.2500
9	0.0156	0.2500	0.2500	0.9844	0.7500	0.7500
10	0.6250	0.3750	0.4583	0.3750	0.6250	0.5417
11	0.2344	0.2500	0.4167	0.7656	0.7500	0.5833
12	0.7813	0.9063	0.8333	0.2188	0.0938	0.1667
13	0.0000	0.0000	0.3333	1.0000	1.0000	0.6667
14	0.5938	0.0625	0.7083	0.4063	0.9375	0.2917
15	0.4844	0.1875	0.5417	0.5156	0.8125	0.4583
16	1.0000	0.8125	0.8333	0.0000	0.1875	0.1667
17	0.0469	0.0000	0.0000	0.9531	1.0000	1.0000
18	0.7500	0.4688	0.8542	0.2500	0.5313	0.1458
19	0.2969	0.1250	0.2500	0.7031	0.8750	0.7500
20	0.7500	0.9375	0.7500	0.2500	0.0625	0.2500
21	0.6094	0.5625	0.7083	0.3906	0.4375	0.2917
22	0.4375	0.4375	0.5833	0.5625	0.5625	0.4167
23	0.5313	0.7500	0.8750	0.4687	0.2500	0.1250
24	0.4125	0.2500	0.4375	0.5875	0.7500	0.5625
25	0.4531	0.5625	0.6875	0.5469	0.4375	0.3125
26	0.5156	0.6250	0.6458	0.4844	0.3750	0.3542
27	0.4531	0.5625	0.6875	0.5469	0.4375	0.3125
28	0.5938	0.6250	0.6458	0.4063	0.3750	0.3542
29	0.5313	0.5625	0.6875	0.4687	0.4375	0.3125
30	0.5938	0.6250	0.6458	0.4063	0.3750	0.3542
31	0.4844	0.6875	0.7083	0.5156	0.3125	0.2917

Table 7. Grey relational coefficient and Grey relational grade of Each performance characteristics ($\zeta = 0.5$)

Experiment No.	Grey Relation Coefficient			Grey Relation Grade	Rank
	Grain size	Hardness	UTS		
1	0.571	0.421	0.500	0.497	
2	0.615	0.552	1.000	0.722	
3	0.492	0.571	0.600	0.555	
4	0.577	0.889	0.750	0.738	
5	0.471	0.400	0.500	0.457	
6	0.383	0.500	0.632	0.505	
7	0.525	0.615	0.444	0.528	
8	0.471	1.000	0.667	0.712	
9	0.337	0.400	0.400	0.379	
10	0.571	0.444	0.480	0.499	
11	0.395	0.400	0.462	0.419	
12	0.696	0.842	0.750	0.763	
13	0.333	0.333	0.429	0.365	
14	0.552	0.348	0.632	0.510	
15	0.492	0.381	0.522	0.465	
16	1.000	0.727	0.750	0.826	1
17	0.344	0.333	0.333	0.337	
18	0.667	0.485	0.774	0.642	
19	0.416	0.364	0.400	0.393	
20	0.667	0.889	0.667	0.741	
21	0.561	0.533	0.632	0.575	
22	0.471	0.471	0.545	0.496	
23	0.516	0.667	0.800	0.661	
24	0.460	0.400	0.471	0.443	
25	0.478	0.533	0.615	0.542	
26	0.508	0.571	0.585	0.555	
27	0.478	0.533	0.615	0.542	
28	0.552	0.571	0.585	0.570	
29	0.516	0.533	0.615	0.555	
30	0.552	0.571	0.585	0.570	
31	0.492	0.615	0.632	0.580	

Table 8. Response table (mean) for overall grey relational grade

LEVEL	Peak Current	Base Current	Pulse Rate	Pulse Width
1	0.3369	0.3931	0.5754	0.6609
2	0.4581	0.4918	0.5715	0.5894
3	0.5526	0.5305	0.5394	0.5347
4	0.6594	0.6257	0.5461	0.5282
5	0.6419	0.7407	0.4955	0.4435
Delta	0.3225	0.3477	0.0799	0.2175
Rank	2	1	4	3

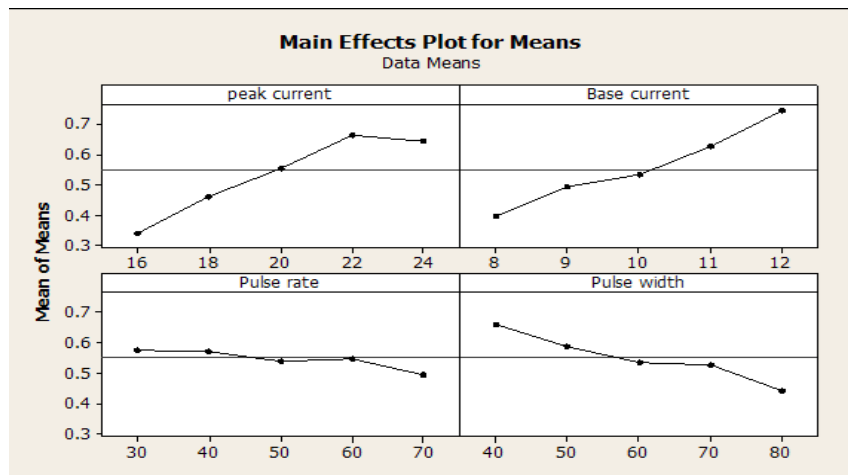


Figure 8. Effect of welding parameters on grey relational grade.

3.4 Confirmation Experiments for Grey Relational Analysis

After evaluating the optimal parameter settings, the next step is to predict and verify the enhancement of quality characteristics using the optimal parametric combination. Table 9 shows the comparison of the predicted weld bead geometry parameters with that of actual using the optimal MPAW welding conditions. There is a good agreement between the actual and predicted results (improvement in the overall Grey relational grade).

Table 9. Results of confirmation test for Grey Relational Analysis

	Initial Values	Experimental Values
Combination	A-4,B-5,C-1,D-1	A-5,B-4,C-4,D-3
Grain Size	63.6	67.9
Hardness	273	284
UTS	546	584
Grey Relation Grade	0.826	0.884

From Table 9, it is understood that utilization of the optimal welding parameter combination enhances the grey relational grade from 0.826 to 0.884, i.e. grey relational grade has improved by 5.8%.

4. Conclusions

The following conclusions are drawn based on the experiments performed.

1. AISI 904L super austenitic steels are butt welded using Micro Plasma Arc Welding at different combinations as per the RSM-CCD Design Matrix.
2. As per Response Surface Method at a peak current of 24 Amperes, Base current of 12 Amperes, pulse rate of 70 pulses/sec and pulse width of 80%, the optimal grain size is 49.7257 Microns, Hardness is 270.0476 VHN and UTS is 558.4762MPa. The optimal combination obtained is not within the 31 combination of experiments performed (Table 5). However, they are within the selected range of welding parameter (Table 4).
3. The optimal performance for grain size, hardness and UTS are obtained for the following combination of input parameters: Peak current 22 Amps, Back Current 11 Amps, Pulse Rate 60 pulses/sec, Pulse Width 70%. The optimal combinations of input welding parameters are within the chosen 31 combination of experiments (Table 5).
4. The order of importance of the welding parameters is base current, peak current, pulse width and pulse rate.
5. An improvement of 5.8% is obtained in Grey Relational Grade.

5. Acknowledgement

We are thankful to Metallic Bellows(I) PvtLtd , Chennai, India for providing the experimental facility.

Conflict of interest

The authors declare no conflict of interest.

References

- [1] Deepashri D. Nage, V. S. Raja, Effect of nitrogen addition on the microstructure and mechanical behaviour of 317L and 904L austenitic stainless-steel welds, *J Mater Sci*, 41(20), 2006, 97-2112.
- [2] Barbara Nasilowska, Zdzislaw Bogdanowicz, Michal Wojucki, Shot peening effect on 904L welds corrosion resistance, *Journal of Constructional Steel Research*, 115, 2015, 276–282.
- [3] D.D. Nage and V. S. Raja, Examination of Crater Crack Formation in Nitrogen-Containing Austenitic Stainless-Steel Welds, *welding research*, 2017, 104-112.
- [4] K. Devendranath Ramkumar, Akash Harendra Dagur, Ashwin Anil Kartha, Moharil Atharva Subodh, C. Vishnu, D. Arun, M. Giridharan Vijay Kumar, Winston Sunny Abraham, Ankita Chatterjee, Jayanthi Abraham, Johann Abraham, Microstructure, mechanical properties and biocorrosion behaviour of dissimilar welds of AISI 904L and UNS S32750, *Journal of Manufacturing Processes* 30, 2017, 27-40.
- [5] P. Sathiyaa, S. Aravindan, P.M. Ajith, B. Arivazhagan, A. Noorul Haq, Microstructural characteristics on bead on plate welding of AISI 904L super austenitic stainless steel using Gas metal arc welding process, *International Journal of Engineering, Science and Technology*, 2(6), 2010, 189-199.
- [6] K. Devendranath Ramkumar, Jelli Lakshmi Narasimha Varma, Gangineni Chaitanya, Ayush Choudhary, N. Arivazhagan, S. Narayanan, Effect of autogeneous GTA welding with and without flux addition on the microstructure and mechanical properties of AISI 904L joints, *Materials Science & Engineering A*, 636, 2015, 1-9.
- [7] P. Manavalan and S. Ravi, R. Kesavan, Identification of optimized welding conditions for pulsed current gas metal arc welding of AISI 904 super austenitic stainless steel, *Applied Mechanics and Materials*, 787, 2015, 500-504.
- [8] K. Devendranath Ramkumar, Ayush Choudhary, Shivang Aggarwal, Anubhav Srivastava, Tadikonda Harsha Mohan, and N. Arivazhagan, Characterization of microstructure and mechanical properties of continuous and pulsed current gas tungsten arc welded super austenitic stainless steel, *Materials Research Society*, 2015, 1-20.
- [9] K. Devendranath Ramkumar, Shah Vitesh Naren, Venkata Rama Karthik Paga, Ambuj Tiwari, N. Arivazhagan, Development of pulsed current gas tungsten arc welding technique for dissimilar joints of marine grade alloys, *Journal of Manufacturing Processes*, 383, 2015, 1-13.
- [10] Kondapalli Siva Prasad, Ch. Srinivasa Rao, D. Nageswara Rao, Optimization of fusion zone grain size, hardness and ultimate tensile strength of pulsed current micro plasma arc welded Inconel 625 sheets using genetic algorithm, *International Journal of Advanced Manufacturing Technology* (Springer), Volume 85, Issue 8-12, 2287-2295.
- [11] Kondapalli Siva Prasad, Ch. Srinivasa Rao, D. Nageswara Rao, Optimizing Fusion Zone Grain Size and Ultimate Tensile Strength of Pulsed Current Micro Plasma Arc Welded Inconel 625 Alloy Sheets using Hooke & Jeeves Method, *International Transaction Journal of Engineering, Management & Applied Sciences & Technologies*, Volume 3, No.1, 2012, 87-100.
- [12] Kondapalli Siva Prasad, Ch. Srinivasa Rao, D. Nageswara Rao, Effect of pulsed current micro plasma arc welding process parameters on fusion zone grain size and ultimate tensile strength of Inconel 625 sheets, *Acta Metallurgica Sinica* (English letters), Volume 25, Number 3, 2012, 179-189.