



Research Article

Methanol to Gasoline Conversion over CuO/ZSM-5 Catalyst Synthesized and Influence of Water on Conversion

Ehsan Kianfar^{*ID}, Mahmoud Salimi^{ID}, Behnam Koohestani

Department of Chemical Engineering, Arak Branch, Islamic Azad University, Arak, Iran
E-mail: e-kianfar94@iau-arak.ac.ir

Received: 21 June 2020; **Revised:** 4 September 2020; **Accepted:** 4 September 2020

Abstract: Conversion of Methanol to Gasoline (MTG) process is accomplished by the synthesis of a ZSM-5 zeolite catalyst to produce high-quality gasoline. The generated catalyst had surface areas of Zeolite and CuO/ZSM-5 (2%) and CuO/ZSM-5 (4%) of $300 \text{ m}^2 \cdot \text{g}^{-1}$, $284 \text{ m}^2 \cdot \text{g}^{-1}$ and $254 \text{ m}^2 \cdot \text{g}^{-1}$. Structure and morphology of synthesized catalysts were studied by such analyses as Brunauer-Emmett-Teller (BET), X-Ray Fluorescence (XRF), Scanning Electron Microscope (SEM), and X-Ray Diffraction (XRD). CuO/ZSM-5 (4%) (70% water/30% methanol feed) catalyst resulted in increased activity for the conversion of methanol to hydrocarbons of the gasoline range, especially aromatics. Using (70% water/30% methanol feed) with catalyst CuO/ZSM-5 (4%) led to improved performance of catalysts and increased aromatic and decreased conversion. The main aromatic products were C_7H_8 , $(\text{CH}_3)_2\text{C}_6\text{H}_4$, C_8H_{10} , $\text{CH}_3\text{C}_6\text{H}_4\text{C}_2\text{H}_5$, $\text{C}_{10}\text{H}_{14}$, $\text{C}_6\text{H}_4(\text{C}_2\text{H}_5)_2$, and $\text{C}_6\text{H}_5(\text{CH}_2)_3\text{CH}_3$. Also, water on ZSM-5 and CuO/ZSM-5 plays an important role in the formation of aromatic products.

Keywords: ZSM-5 zeolite catalyst, fixed-bed reactor, specific surface, water, sonochemistry

1. Introduction

The zeolites are crystal aluminum silicates and hydrated alkaline metals and alkaline earth which contain the 3D network which is composed of $[\text{SiO}_4]^{4-}$ and $[\text{AlO}_4]^{4-}$ tetrahedrons. Such catalysts are used in Fluid Catalytic Cracking (FCC), hydrocracking, desulfurization of gasoline, isomerization of light paraffin, Methanol to Gasoline, or Gasoil conversion, and Methanol to Propylene (MTP) and methanol to Dimethyl Ether (DME) processes.¹⁻⁴ Among all these acidic catalysts, ZSM-5 with medium size and porosity is more applied in petrochemical industries. The high efficiency of Zeolites as a catalyst is due to high morphology and its special properties including a specific crystalline structure, high level, uniform pores, high thermal stability, and selectivity which result in the formation of the proper catalyst.⁵⁻⁷ In refineries, Zeolite catalysts are the main source of gasoline and octane efficiency improvement as well as the production of lubricants and clean fuel. There is plenty of evidence that shows that limited petroleum resources are not able to supply global energy demands. General consumption of fuel is about 116.45 million tons per day which is being increased with a growth of more than 3%. Given this rate, consumption will reach 162.28 million tons per day in 2020.^{8,9} Conventional methods for gasoline production generally are crude oil distillation and such processes as alkylation and catalytic cracking, although the process of converting coal to liquid is conducted in some countries with coal resources. Given the critical importance and urgent need for fuel as well as increasing demand for fuel, some

alternative methods should be found to produce it. Methanol to Gasoline process, which is a part of the general process of gas to a liquid, is a suitable alternative process. Since gasoline is often used in transportation and production of crude oil and it is going to be terminated with current consumption trends.¹⁰⁻¹² Given the limited current global petroleum resources, it seems necessary to find modern practices to produce valuable fuels like gasoline. One of these practices is MTG. So far, plenty of efforts have been accomplished to produce diverse hydrocarbons through methanol.¹³⁻¹⁷ The conducted studies include an evaluation of the process, catalyst, and operational conditions to implement the reactions. Among Zeolite catalysts, ZSM-5 and SAPO-34 are suitable for the accomplishment of this process and they have been studied more frequently. The main recognized mechanism for the MTG process is Methanol to Dimethyl ether which is an equilibrium reaction and the following rehydration, it is converted to light olefins such as ethylene and propylene.¹⁸⁻²² These olefins are converted to aromatics inside pores of the catalyst and other hydrocarbons are converted to gasoline within the boiling point range.²³⁻²⁶ With measured volumetric flow and molar composition of the gaseous product at ambient temperature and pressure, gas density and mass flow were calculated via literature correlations and by known mass flows and compositions (weight percent) of oil cut and aqueous solution, conversion and each component mass percent in whole products can be calculated by mass balance. Methanol conversion was calculated through equations (1) and (2):²⁷⁻³¹

$$X_{\text{MeOH}} = \frac{F_{\text{MeOH}_{\text{in}}} - (F_{\text{MeOH}_{\text{out}}} + 2F_{\text{DME}})}{F_{\text{MeOH}_{\text{in}}}} \quad (1)$$

$$X_{\text{MeOH}} = \frac{\dot{M}_{\text{MeOH}_{\text{in}}} - (\dot{M}_{\text{MeOH}_{\text{out}}} + 1.391\dot{M}_{\text{DME}})}{\dot{M}_{\text{MeOH}_{\text{in}}}} \quad (2)$$

The main aim of the present investigation is to study the effect of CuO loading on ZSM-5 support for conversion of methanol to gasoline range hydrocarbons. A series of CuO/ZSM-5 catalysts were prepared, characterized and experimented for their performance on methanol conversion and hydrocarbon yield. The effects of run time on methanol conversion and hydrocarbon yield with various CuO/ZSM-5 catalysts have been studied. Zeolites as catalysts have many unique properties such as acidity, shape-selectivity, high surface area and structural stability.

2. Materials and methods

2.1 Materials

Sodium aluminate (technical grade) was purchased Riedel-deHaen. Silicic acid (96.6%), tetrapropylammonium bromide (98%), sodium hydroxide (97.5%), methanol (99.9%), ethanol (96%), and copper (II) nitrate (99.9%) ammonium nitrate (99.95%) was supplied by Merck. All the chemicals used in this research were of analytical grade.

3. Zeolite catalyst synthesis and CuO/ZSM-5

Gel Preparation: The preparation zeolite catalyst, tetrapentyl ammonium bromide was diluted with H₂O and stirred for 20 min. The template was added to the blend of Tetraethyl orthosilicate and H₂O via a syringe pump. Prepared blended stirred on a hot-plate at 40 °C and 300 RPM for 3 hrs. Now, Na₂Al₂O₄ and H₂O added together in another Beaker, and the rest of NaOH was injected into Na₂Al₂O₄ blend followed by roughly stirring for 3 hrs. The second blended added to the first solution drop-wise in 3 hrs, then agitated for 1 hour. As the pH of the prepared Gel has to be adjusted at 10, sulfuric acid was employed as an acidity control agent. The aging session performed for the gel at 400 °C and 300 RPM for 25 hrs. The prepared gel was transferred into a 180 ml Teflon lined autoclave and kept at 180 °C for 50 hrs, using a programmable lab oven. Synthesized catalyst powder was obtained after several times washing with distilled H₂O till pH value reached 7. **Drying & calcination:** Prepared catalyst was dried overnight at 90 °C and then calcined at 50 °C for 10 hrs. The resultant product was dried at 110 °C for 12 hours and calcined at 500 °C for 5 hours.^{8,9}

4. Reactor test

Figure 1 shows the Process Flow Diagram (PFD) of the experimental rig. To carry out experimental runs in the MTG reaction, 1.5 g of the calcined sample with 4 g of Sic were loaded in the catalyst bed under atmospheric pressure. Before feeding the fixed bed reactor, an N₂ flow at 550 °C was passed through the loaded sample for 1 hour to dehumidify and to activate the catalyst. After that, the temperature was regulated to the reaction temperature of 425 °C. The output products of the reaction were analyzed by a gas online chromatography (Agilent GC 7890A) which was equipped with a Flame Ionization Detector (FID) and a Thermal Conductivity Detector (TCD).

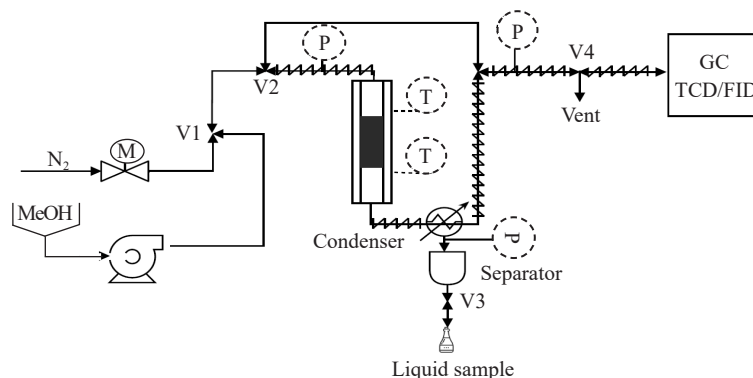


Figure 1. Experimental system for evaluation of ZSM-5 catalyst synthesis performance for methanol to gasoline conversion

5. Results and discussion

5.1 Characterization analysis

5.1.1 XRD analysis

Figure 2 X-Ray Diffraction (XRD) images to determine the crystalline phase, phase purity and crystallinity are the catalysts synthesized. By comparing the obtained patterns and the reference patterns, we conclude all samples had ZSM-5 angles of 8-10 °C¹⁰ sharp peaks at 8, 9, 10, 11, 14, 14.7, 23.1, 24 and 32 crystal faces, respectively.^{8,9} The crystallite sizes were determined peak via Scherrer's equation that is indicated in Table 1.

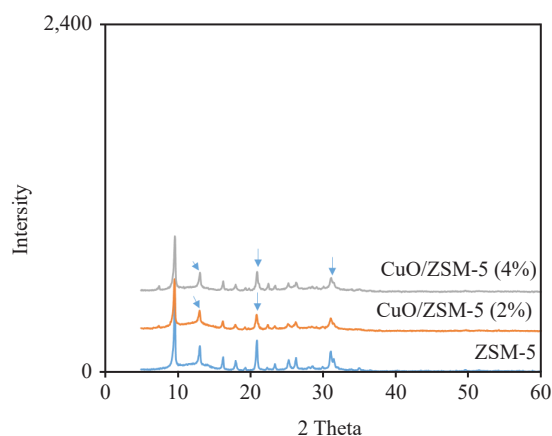


Figure 2. XRD patterns of the parent


Table 1. Results of Brunauer-Emmett-Teller (BET) analysis

Catalyst	Si/Al	SiO ₂ /Al ₂ O ₃	BET surface area (m ² /g)	Crystal size (nm)	Pore volume (cm ³ /g)
ZSM-5	15	30	300	17	0.38
CuO/ZSM-5 (2%)	11	22	278	29	0.35
CuO/ZSM-5 (4%)	10	20	250	30	0.32

Catalyst	V _{Total} /cm ³ ·g ⁻¹	V _{Micro} /cm ³ ·g ⁻¹	V _{Meso} /cm ³ ·g ⁻¹
ZSM-5	0.417	0.102	0.315
CuO/ZSM-5 (2%)	0.315	0.101	0.214
CuO/ZSM-5 (4%)	0.214	0.100	0.115

5.1.2 SEM and EDX analysis

SEM and EDX were used to study the morphology shape and size of the synthesized crystals. Figures 3-4 and Table 2 show the images of the SEM for 3 synthesized samples. The SEM images of the samples show that the morphology of all the samples as expected for ZSM-5 is regular and the dominant phase in all samples is ZSM-5, CuO/ZSM-5 (2%), and CuO/ZSM-5 (4%). Considering pH and surface specifications such as isoelectric charge, there is an obvious possibility for metal deposition out of the frame and/or catalyst pores. This distribution leads to catalyst malfunction which shall be fast deactivation, lower conversion, and product selectivity reduction.

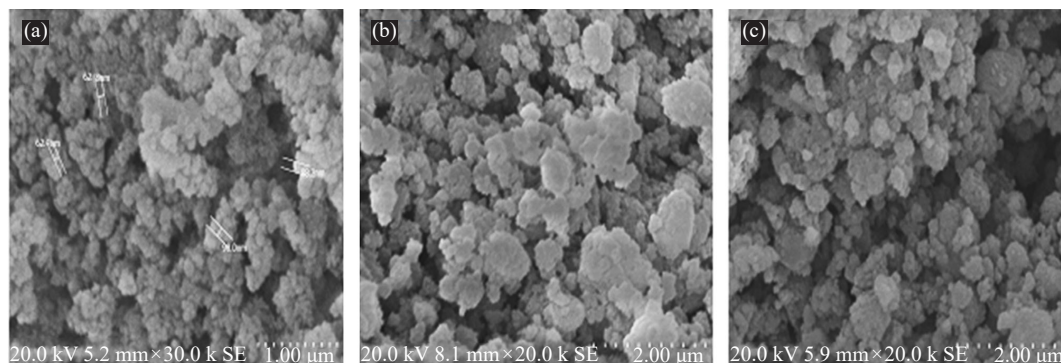**Figure 3.** SEM patterns of the parent (a) ZSM-5, (b) CuO/ZSM-5 (2%), (c) CuO/ZSM-5 (4%)**Table 2.** EDX pattern for promoted/pure catalyst batches

Element	Pure	CuO (2%)	CuO (4%)
Elemental analysis	O	65.4	66.8
	Al	0.82	0.78
	Si	33.78	32.3
	CuO	0	0.12

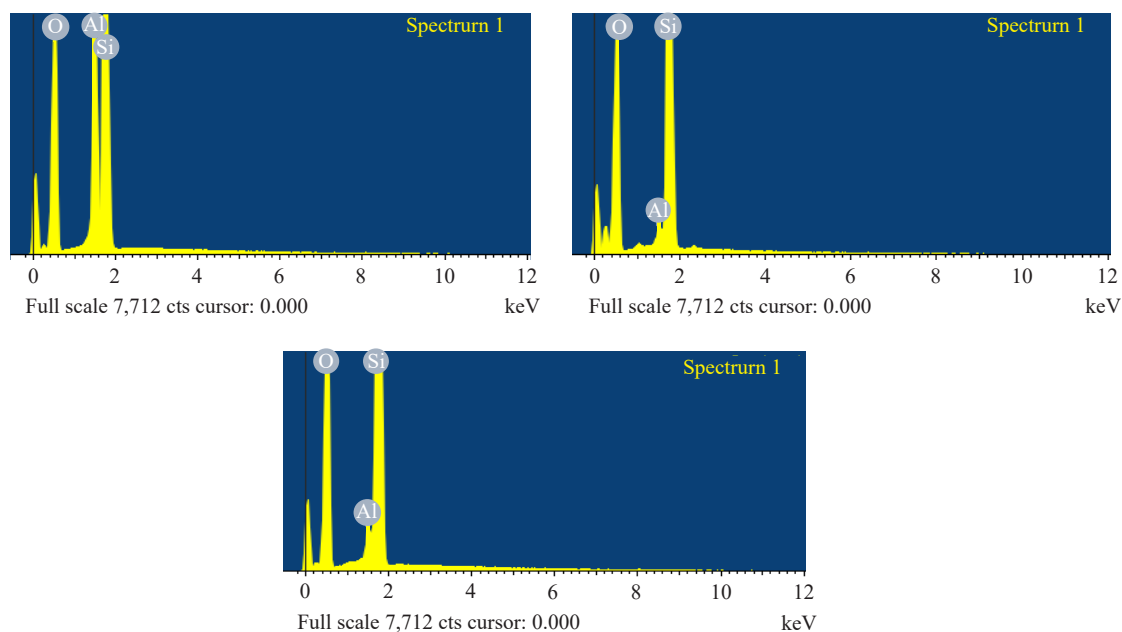


Figure 4. EDX pattern for promoted/pure catalyst batches

5.1.3 TPD analysis

The synthesized catalyst was studied using Micrometrics Autochem 2920 unit (equipped with TCD) to determine acidity and acid site distribution operates with He as carrier and ammonia during adsorption. The sample preparation was performed at 500 °C for 2 hours followed by cooling at 100 °C. Figure 5 illustrates the TPD results of parent ZSM-5 zeolite over temperature range of 100 to 900 °C. Two main peaks are observed with maximum at 200 °C and 415 °C, which is attributed to weak/medium and strong acid sites, respectively. The results of TPD analysis are suitably in line with the aluminum presence in Zeolite composition.⁸

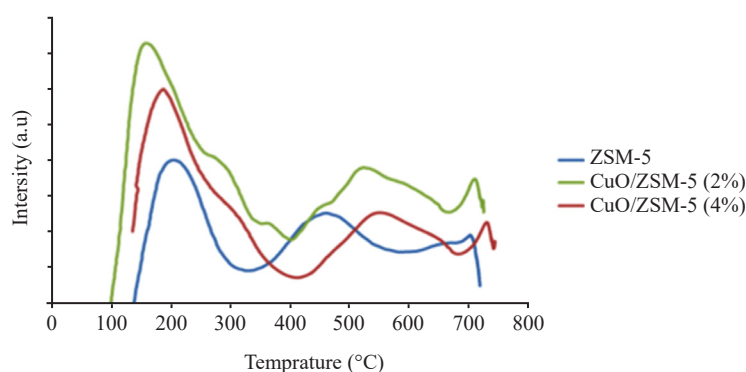


Figure 5. NH₃-TPD analysis for prepared catalyst

5.1.4 N₂ adsorption-desorption isotherms analysis

Figure 6 shows N₂ adsorption-desorption which is used to determine the porosity, specific surface area, and physisorption isotherms. All samples exhibit a typical reversible type IV adsorption isotherm as defined by International Union of Pure and Applied Chemistry (IUPAC). The hysteresis loop is very similar to the H₃ type N₂ adsorption-

desorption isotherms with hysteresis characterization. Three different stages are observed in the isotherms. At low relative pressure ($P/P_0 < 0.4$), adsorption occurs only as of the monolayer on the pore walls. As the relative pressure increases ($P/P_0 > 0.4$), a hysteresis loop is observed which is a characteristic of capillary condensation of nitrogen in mesoporous. At higher pressure ($P/P_0 > 0.95$), again another linear region is observed. This part is attributed to the multilayer N_2 adsorption on the external surface of the materials. There is no limiting uptake observed over the high range of P/P_0 , which is characteristic of aggregates with plate-like particles.^{8,32}

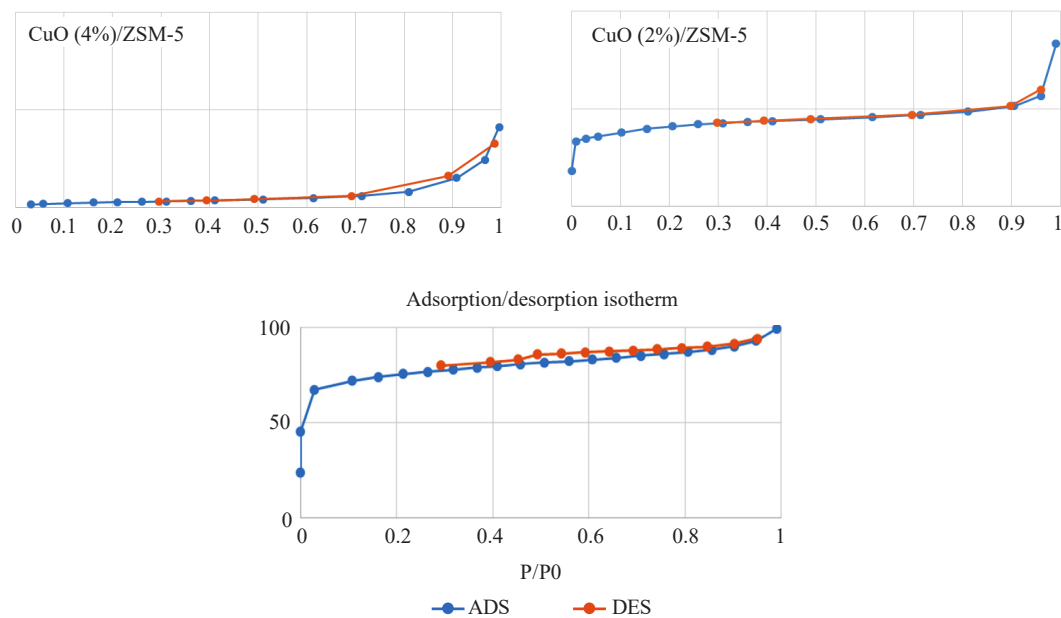


Figure 6. N_2 adsorption-desorption isotherms

5.1.5 Catalyst performance

Table 3. The selectivity of produced gasoline hydrocarbons

Compound	ZSM-5	CuO/ZSM-5 (2%)	CuO/ZSM-5 (4%)
Methanol input (%)	100	30	30
Conversion (mol%)	99.5	94.6	93.3
Aromatics	40	65	75
Iso-paraffins	7.5	2.5	2.5
Naphthenes	2.0	3.6	2.3
Olefins	34.0	5.4	2.8
Paraffins	2	2.0	0.8
Unknown	1	4.5	4.9

Table 3 compare selectivity of production of gasoline hydrocarbon groups by using the catalyst of CuO (4%)/ZSM-5 and input methanol ratios of 30% and 100%. A major portion of produced gasoline compositions is dedicated to

aromatics by using methanol feed of 30% while lower light olefin compositions and lower conversions are seen. Table 4 compare selectivity of production of gasoline hydrocarbons. As it can be seen from the Table 4, using methanol feed of 30%, the rate of the hydrocarbons heavier than octane was significantly increased. Table 4 shows the selectivity of the produced gasoline hydrocarbons, demonstrating a lower amount of olefin and light alkanes and heavier aromatics, especially xylene and ethyl toluene. Therefore, using a methanol feed of 30%, the process is argued to be improved and the final reaction of heavier hydrocarbons and aromatics production was substantially increased, which may be due to higher methanol rate over the catalyst or burning coke with water steam and catalyst recovery during the process. Table 4 major portion of produced gasoline compositions is dedicated to aromatics by using catalysts CuO/ZSM-5 (4%) with methanol feed of 30% while lower light olefin compositions and increased Xylene are seen.

Table 4. The selectivity of produced gasoline hydrocarbons

Compound	ZSM-5	CuO/ZSM-5 (2%)	CuO/ZSM-5 (4%)
Methanol input (%)	100	30	30
	Yield (%)		
Benzene	1.3	0.4	0.1
Toluene	6.4	6.5	3.8
Xylene	28.0	45.1	56.7
Ethylbenzen	1.2	1.3	1.6
Ethyltoluene	3.3	3.5	5.8
Propylbenzene	0.1	0.2	0.3
Ethyl dimethylbenzene	0.1	0.2	0.4
Trimethylbenzene	0.4	2.7	1.9
Diethylbenzene	0.4	0.5	0.7
Butylbenzene	2.8	2.5	7.9
Olefins	37.0	35.0	15.5
Water	19	2.1	5.3

6. Conclusion

This work shows that zeolite has a good effect on the transformation of methanol to gasoline. Noticeable growth in selectivity to aromatics and higher hydrocarbons was observed over the ZSM-5 catalyst, which was prepared using sonication. CuO/ZSM-5 (4%) (70% water/30% methanol feed) catalyst resulted in increased activity for the conversion of methanol to hydrocarbons of the gasoline range especially aromatics. Using a 30% methanol feed with catalyst CuO/ZSM-5 (4%) led to improved performance of catalysts and increased aromatic and decreased conversion. The main aromatic products were C_7H_8 , $(CH_3)_2C_6H_4$, C_8H_{10} , $CH_3C_6H_4C_2H_5$, $C_{10}H_{14}$, $C_6H_4(C_2H_5)_2$, and $C_6H_5(CH_2)_3CH_3$. Also, water on ZSM-5 and CuO/ZSM-5 plays an important role in the formation of aromatic products.

Conflict of interest

The authors declare that they have no conflict of interest.

References

- [1] Aboul-Gheit, A. K.; Ghoneim, S. A. Catalysis in the petroleum naphtha catalytic reforming process. *Recent Patents on Chemical Engineering* **2008**, *1*, 113-125.
- [2] Abu-Zied, B. M.; Schwieger, W.; Unger, A. Nitrous oxide decomposition over transition metal exchanged ZSM-5 zeolites prepared by the solid-state ion-exchange method. *Appl. Catal. B Environ.* **2008**, *84*, 277-288.
- [3] Armaroli, T.; Simon, L. J.; Digne, M.; Montanari, T.; Bevilacqua, M.; Valtchev, V.; Patarin, J.; Busca, G. Effects of crystal size and Si/Al ratio on the surface properties of H-ZSM-5 zeolites. *Appl. Catal. A: Gen.* **2006**, *306*, 78-84.
- [4] Benito, P. L.; Gayubo, A. G.; Aguayo, A. T.; Olazar, M.; Bilbao, J. Effect of Si/Al ratio and of acidity of H-ZSM5 zeolites on the primary products of methanol to gasoline conversion. *J. Chem. Tech. Biotechnol.* **1996**, *66*, 183-191.
- [5] Bibby, D. M.; Russell, F.; McLellan, G. D. Coke formation in high-silica zeolites. *Appl. Catal. A: Gen.* **1992**, *93*, 1-34.
- [6] Bjorgen, M.; Joensen, F.; Holm, M. S.; Olsbye, U.; Lillerud, K. P.; Svelle, S. Methanol to gasoline over zeolite H-ZSM-5: Improved catalyst performance by treatment with NaOH. *Appl. Catal. A: Gen.* **2008**, *345*, 43-50.
- [7] Bjorgen, M.; Joensen, F.; Lillerud, K. P.; Olsbye, U.; Svelle, S. The mechanisms of ethene and propene formation from methanol over high silica H-ZSM-5 and H-beta. *Catal. Today* **2009**, *142*, 90-97.
- [8] Bjorgen, M.; Svelle, S.; Joensen, F.; Nerlov, J.; Kolboe, S.; Bonino, F.; Palumbo, L.; Bordiga, S.; Olsbye, U. Conversion of methanol to hydrocarbons over zeolite H-ZSM-5: On the origin of the olefinic species. *J. Catal.* **2007**, *249*, 195-207.
- [9] BP Plc. *BP Statistical Review of World Energy*; London, UK, 2019.
- [10] Burgfels, G.; Schönlinner, J.; Schmidt, F. Process for Producing Synthetic Zeolites with an MFI Structure. U.S. Patent 6,951,638 B1, October 4, 2005.
- [11] Cejka, J.; Corma, A.; Zones, S. *Zeolites and Catalysis: Synthesis, Reactions and Applications*; Wiley, 2001.
- [12] Kianfar, E.; Salimi, M.; Pirouzfard, V.; Koohestani, B. Synthesis and modification of zeolite ZSM-5 catalyst with solutions of calcium carbonate (CaCO_3) and sodium carbonate (Na_2CO_3) for methanol to gasoline conversion. *Int. J. Chem. React. Eng.* **2018**, *16*(7), 1-7.
- [13] Kianfar, E.; Salimi, M.; Hajimirzaee, S.; Koohestani, B. Methanol to gasoline conversion over CuO/ZSM-5 catalyst synthesized using sonochemistry method. *Int. J. Chem. React. Eng.* **2019**, *17*(2), 1-10.
- [14] Kianfara, E. Synthesis and characterization of $\text{AlPO}_4/\text{ZSM-5}$ catalyst for methanol conversion to dimethyl ether. *Russ. J. Appl. Chem.* **2018**, *91*(10), 1710-1720.
- [15] Kianfara, E. Nanozeolites: Synthesized, properties, applications. *J. Sol-Gel Sci. Technol.* **2019**, *91*(2), 415-429.
- [16] Kianfara, E.; Salimi, M.; Pirouzfard, V.; Koohestani, B. Synthesis of modified catalyst and stabilization of CuO/ $\text{NH}_4\text{-ZSM-5}$ for conversion of methanol to gasoline. *Int. J. Appl. Ceram. Technol.* **2018**, *15*(3), 734-741.
- [17] Kianfara, E. Comparison and assessment of zeolite catalysts performance dimethyl ether and light olefins production through methanol: A review. *Rev. Inorg. Chem.* **2019**, *39*(3), 157-177.
- [18] Kianfara, E. Ethylene to propylene over zeolite ZSM-5: Improved catalyst performance by treatment with CuO. *Russ. J. Appl. Chem.* **2019**, *92*(7), 933-939.
- [19] Kianfara, E. Ethylene to propylene conversion over Ni-W/ZSM-5 catalyst synthesize. *Russ. J. Appl. Chem.* **2019**, *92*(8), 1094-1101.
- [20] Kianfara, E. Zeolite-based catalysts for methanol to gasoline process: A review. *Microchem J.* **2019**, *156*, 104822.
- [21] Kianfara, E.; Salimi, M. A review on the production of light olefins from hydrocarbons cracking and methanol conversion. *Adv. Chem. Res.* **2020**, *59*(1), 1-81.
- [22] Kianfara, E.; Razavi, A. Zeolite catalyst based selective for the process MTG: A review. In *Zeolites: Advances in Research and Applications*; Nova Science Publishers, Inc: NY, USA, 2020.
- [23] Djieugoue, M. A.; Prakash, A. M.; Kevan, L. Electron spin resonance and electron spin-echo modulation studies of synthesized NiAPSO-34 molecular sieve and comparison with ion-exchanged NiH-SAPO-34 molecular sieve. *J. Phys. Chem. B* **1999**, *103*(5), 804-811.
- [24] Cola, P. L. D.; Gläser, R.; Weitkamp, J. Non-oxidative propane dehydrogenation over Pt-Zn-containing zeolites. *Appl. Catal. A: Gen.* **2006**, *306*(7), 85-97.

- [25] Hochtl, M.; Jentys, A.; Vinek, H. Isomerization of 1-pentene over SAPO, CoAPO (AEL, AFI) molecular sieves and HZSM-5. *Appl. Catal. A: Gen.* **2001**, 207(1-2), 397-405.
- [26] Wilson, S.; Barger, P. The characteristics of SAPO-34 which influence the conversion of methanol to light olefins. *Micropor. Mesopor. Mat.* **1999**, 29(1-2), 117-126.
- [27] Dahl, I. M.; Mostad, H.; Akporiaye, D.; Wendelbo, R. Structural and chemical influences on the MTO reaction: A comparison of chabazite and SAPO-34 as MTO catalysts. *Micropor. Mesopor. Mat.* **1999**, 29(1-2), 185-190.
- [28] Sastre, G.; Lewis, D. W.; Richard, C.; Catlow, A. Modeling of silicon substitution in SAPO-5 and SAPO-34 molecular sieves. *J. Phys. Chem. B* **1997**, 101(27), 5252-5262.
- [29] Hajiashrafi, T.; Kharat, A. N. Study of preparation methods and their effect on the morphology and texture of SAPO-34 for the methanol to olefin reaction. *React. Kinet. Mech. Catal.* **2013**, 108(2), 417-432.
- [30] Emrani, P.; Fatemi, S.; Talesh, S. A. Effect of synthesis parameters on phase purity, crystallinity and particle size of SAPO-34. *Iran. J. Chem. Chem. Eng.* **2011**, 30(4), 29-36.
- [31] Tan, J.; Liu, Z.; Bao, X.; Liu, X.; Han, X.; He, C.; Zhai, R. Crystallization and Si incorporation mechanisms of SAPO-34. *Micropor. Mesopor. Mat.* **2002**, 53(1-3), 97-108.
- [32] Zibrowius, B.; Löffler, E.; Hunger, M. Multinuclear MAS n.m.r. and i.r. spectroscopic study of silicon incorporation into SAPO-5, SAPO-31, and SAPO-34 molecular sieves. *Zeolites* **1992**, 12(2), 167-174.